arXiv:cond-mat/0011381v1 [cond-mat.supr-con] 22 Nov 2000

Isotope effects in underdoped cuprate superconductors: a quantum critical phenomenon

T. Schneider and H.Keller
Physik-Institut der Universität Zürich, Winterthurerstr. 190,
CH-8057 Zürich, Switzerland

(February 1, 2008)

We show that the unusual doping dependence of the isotope effects on transition temperature and zero temperature in - plane penetration depth naturally follows from the doping driven 3D-2D crossover, the 2D quantum superconductor to insulator transition (QSI) in the underdoped limit and the change of the relative doping concentration upon isotope substitution. Close to the QSI transition both, the isotope coefficient of transition temperature and penetration depth approach the coefficient of the relative dopant concentration, and its divergence sets the scale. These predictions are fully consistent with the experimental data and imply that close to the underdoped limit the unusual isotope effect on transition temperature and penetration depth uncovers critical phenomena associated with the quantum superconductor to insulator transition in two dimensions.

PACS numbers: 74.20.Mn, 74.25Dw, 5.40.-a

The observation of an unusual isotope effect in underdoped cuprate superconductors on transition temperature [1–3] and zero temperature penetration depth [4–7] poses a challenge to the understanding of high temperature superconductivity. In this letter we show that this behavior naturally follows from the doping driven 3D-2D crossover, the 2D superconductor to insulator (QSI) transition in the underdoped limit and the change of the relative doping concentration upon isotope substitution. Thus, the unusual isotope effect on superconducting properties of underdoped cuprates is derived to be a quantum critical phenomenon driven by variation of the dopant concentration.

Consider the empirical phase diagram of $La_{2-x}Sr_xCuO_4$ [8–16]depicted in Fig.1. It shows that after passing the so called underdoped limit ($x = x_u \approx 0.05$), where the quantum insulator to superconductor (QSI) transition occurs [17,18], T_c rises and reaches a maximum value T_c^m at $x_m \approx 0.15$. With further increase of x, T_c decreases and finally vanishes in the overdoped limit $x_o \approx 0.3$. This phase transition line $T_c(x)$, separating the superconducting from the normal conducting phase, appears to be a generic property of cuprate superconductors. In $La_{2-x}Sr_xCuO_4$, $HgBa_2CuO_{4+x}$ [19,20] and $Bi_2Sr_2CuO_{6+x}$ [21]both, the underdoped and overdoped limits, corresponding to critical endpoints, are experimentally accessible. In other cuprates, including $Bi_2Sr_2CaCu_2O_{8+x}$ [21], $YBa_2Cu_3O_{7-x}$ [22] and $Y_{1-x}Pr_xBa_2Cu_3O_{7-\delta}$ [23], only the underdoped and optimally doped regimes appear to be accessible. As shown in Fig.1 for $La_{2-x}Sr_xCuO_4$ the effective mass anisotropy, measured in terms of $\gamma = \sqrt{M_c/M_{ab}}$ increases drastically by approaching the underdoped limit. This property, also observed in $HgBa_2CuO_{4+\delta}$ [20] and $YBa_2Cu_3O_{7-x}$ [22], appears to be generic and reveals the crossover from three (3D) to two dimensional (2D) behavior.

In our considerations the starting point is the critical endpoint of the phase transition line $T_c(x)$, where at $T = 0$ and $x = x_u$, driven by variation of the dopant concentration x, the QSI transition occurs. Close to this critical endpoint the bulk superconductors correspond to a stack of independent superconducting slabs of thickness d_s. Moreover, close to such a critical point, low energy properties depend only on the spatial dimensionality of the system, the number of components of the order parameter and the range of the interaction. The theory of quantum critical phenomena predicts that the transition temperature and zero temperature in - plane penetration depth scale as [24,17,18]

$$T_c = a\ \delta^{z\overline{\nu}}, \qquad \frac{1}{\lambda_{ab}^2(0)} = b\delta^{z\overline{\nu}}. \tag{1}$$

z is the dynamic critical exponent, $\overline{\nu}$ the exponent of the diverging length, a and b nonuniversal critical amplitudes, and

$$\delta = x - x_u \tag{2}$$

measures the distance from the quantum critical point at x_u, where in cuprate superconductors the QSI transition occurs. For a complex scalar order parameter and in D=2 the critical amplitudes a and b and the slab thickness d_s are not independent but related by the universal relation [24,17,18]

$$\lim_{\delta\to 0}\frac{T_c\lambda_{ab}^2(0)}{d_s} = \frac{a}{bd_s} = \frac{1}{\overline{Q}_2}\left(\frac{\Phi_0^2}{16\pi^3 k_B}\right), \tag{3}$$

where $\overline{Q}_2$ is a universal number. Although the experimental data are rather sparse close to the QSI transition, the overall picture turns out to be highly suggestive and provides consistent evidence for the QSI transition in D=2 at the critical endpoint in the underdoped limit with critical exponents $z \approx 1$ and $\overline{\nu} \approx 1$ [17,18]. This estimate is close to theoretical predictions [25,26], from which $z = 1$ is expected for a bosonic system with long-range Coulomb interactions independent of dimensionality and $\overline{\nu} \geq 1 \approx 1.03$ in $D = 2$. In Fig.1 it is seen that $\overline{\nu} \approx 1$ is also consistent with the doping dependence of the effective mass anisotropy $\gamma = \sqrt{M_c/M_{ab}} \propto \delta^{-\overline{\nu}}$.

We are now prepared to explore the implications of the QSI transition on the isotope effect. From the definition of the isotope coefficient

$$\beta_{T_c} = -\frac{m}{T_c}\frac{dT_c}{dm} \tag{4}$$

and Eq. (1) we obtain the scaling expression

$$\beta_{T_c} = \beta_a + \beta_\delta, \tag{5}$$

where

$$\beta_a = -\frac{m}{a}\frac{da}{dm}, \quad \beta_\delta = \frac{z\overline{\nu}}{\delta}\overline{\beta}_\delta, \quad \overline{\beta}_\delta = -m\frac{d\delta}{dm}. \tag{6}$$

Since in the doping regime of interest, isotope substitution lowers the transition temperature [1,3], while the dopant concentration x remains nearly unchanged [6], there is a positive shift of the underdoped limit x_u, and $\overline{\beta}_\delta$ reduces to

$$\overline{\beta}_\delta = -m\frac{d\delta}{dm} \approx m\frac{dx_u}{dm} > 0. \tag{7}$$

Thus, by approaching the QSI transition β_δ diverges as $\beta_\delta \propto \delta^{-1}$ [Eq.(4)] and provided that β_a remains finite, β_{T_c} is predicted to tend to β_δ so that

$$\frac{1}{\beta_{T_c}} \rightarrow \frac{1}{\beta_\delta} = \overline{r}\left(\frac{T_c}{T_c^m}\right)^{1/z\overline{\nu}}, \qquad \overline{r} = \frac{T_c^m}{z\overline{\nu}\overline{\beta}_\delta a^{1/z\overline{\nu}}}. \tag{8}$$

Here we expressed δ in terms of T_c [Eq.(1)] and rescaled T_c by T_c^m, the transition temperature at optimum doping, to reduce variations of T_c between different cuprates [2,3].

To verify this prediction we show $1/\beta_{T_c}$ versus T_c/T_c^m for $La_{1.85}Sr_{0.15}Cu_{1-x}O_4$ [27], $YBa_{2-x}La_xCu_3O_7$ [28] and $Y_{1-x}\,Pr_xBa_2Cu_3O_7$ [29] in Fig.2. As predicted, by approaching the underdoped limit, corresponding to $T_c/T_c^m = 0$, the data collapses on a single curve, consistent with a straight line pointing to the expected value $z\overline{\nu} \approx 1$, yielding the estimate $\overline{r} \approx 6$ and confirming that β_a is finite and $\overline{\beta}_\delta > 0$. Thus, the OSI transition in $D = 2$ accounts naturally for the unusual doping dependence of β_{T_c} and identifies the isotope induced change of the underdoped limit as the main mechanism. Notice that the empirical estimate for $\overline{r}$ implies that the maximum transition temperature is fixed by $T_c^m \approx 6a\,\overline{\beta}_\delta$.

Another important element brought by the QSI transition in D=2 is the universal relation given in Eq. (3). It implies with Eq.(5) that the isotope coefficients of T_c, $1/\lambda_{ab}^2$, critical amplitudes a and b and slab thickness d_s are related by

$$\beta_{T_c} = \beta_{1/\lambda_{ab}^2} + \beta_{d_s} = \beta_a + \beta_\delta, \qquad \beta_a = \beta_b + \beta_{d_s}, \tag{9}$$

where $\beta_F = -\frac{m}{F}\frac{dF}{dm}$ and $F = T_c$, $1/\lambda_{ab}^2$, d_s, a and b. Noticing that β_a was confirmed to be bounded, this is also true for β_b and β_{d_s}. Since β_{T_c} diverges as $\beta_{T_c} = \beta_\delta = (T_c/T_c^m)^{-1/z\overline{\nu}}/\overline{r}$ [Eq.(8], β_{1/λ_{ab}^2} is predicted to approach

$$\beta_{1/\lambda_{ab}^2} = \beta_{T_c} = \beta_\delta = \frac{1}{\overline{r}}\left(\frac{T_c}{T_c^m}\right)^{-1/z\overline{\nu}} \tag{10}$$

close to the QSI transition. Although the experimental data for β_{1/λ_{ab}^2} and β_{T_c} on identical samples are rather sparse, the results shown in Fig.3 for the oxygen isotope effect in $La_{2-x}Sr_xCu_{1-x}O_4$ [6,7] clearly confirm this prediction. Indeed as the underdoped limit is approached the data points tend to the solid line, marking $1/\beta_{T_c} = 1/\beta_{1/\lambda_{ab}^2}$.

In conclusion, we have shown that the strong doping dependence of the isotope effects on transition temperature and zero temperature in - plane penetration depth naturally follows from the doping driven 3D-2D crossover and the 2D quantum superconductor to insulator transition in the underdoped limit. As the quantum superconductor to insulator transition is approached, the isotope coefficient of transition temperature β_{T_c} and penetration depth β_{1/λ_{ab}^2} tend to the coefficient of the relative dopant concentration β_δ, and its divergence sets the scale. These predictions are fully consistent with the experimental data and imply that close to the underdoped limit the unusual isotope effects on transition temperature and penetration depth uncovers critical phenomena, associated with the quantum superconductor to insulator transition in two dimensions. Moreover, since lattice distortions are the primary consequence of isotope substitution it becomes clear that the isotope effects on transition temperature and zero temperature penetration depth probe the effect of lattice degrees of freedom on the condensate. However, until now most of the proposed theories of high temperature superconductivity in the cuprates have considered charge and spin fluctuations in a doped two dimensional (2D) antiferromagnet and disregarded any coupling to the lattice degrees of freedom.

The authors are grateful to K.A. Müller, S. Roos and G.M. Zhao for very useful comments and suggestions on the subject matter. This work was partially supported by the Swiss National Science Foundation.

---

* Corresponding author: T.Schneider
Email address: toni.schneider@swissonline.ch

[1] J.P. Franck, in: Physical Properties of High Temperature Superconductivity IV, ed. D.S.Ginsberg (World Scientific Singapore, 1994 (p.189-293)
[2] T. Schneider and H. Keller, Phys.Rev.Lett. **69**, 3374 (1993)
[3] T. Schneider and H. Keller, Int. J. Mod. Phys. B**8**, 487 (1993)
[4] G.M. Zhao et al, Phys.Rev. B **52**, 6840 (1995)
[5] G.M. Zhao et al, Nature **385**, 236 (1997)
[6] G.M. Zhao et al, J.Phys.Condens.Matter **10**, 9055 (1998)
[7] J. Hofer et al, Phys.Rev.Lett.84, 4192 (2000)
[8] H. Takagi et al, Phys.Rev. B **40**, 2254 (1989)
[9] J.B. Torrance et al, Phys.Rev. B **40**, 8872 (1989)
[10] M. Suzuki and M.Hikita, Phys.Rev. B **44**, 249 (1991)
[11] T.Kimura et al, Physica C **192,** 247 (1992)
[12] N.Yamada and M.Ido, Physica C **203**, 240 (1992)
[13] T. Nagano et al, Phys.Rev. B **48**, 9689 (1993)
[14] Y. Fukuzumi et al, Phys.Rev.Lett. **76**, 684 (1996)
[15] T. Sasagawa et al, Phys.Rev. B **61**, 1610 (2000)
[16] J. Hofer et al, Phys.Rev. B **62,**631 (2000)
[17] T. Schneider and J. M. Singer, *Phase Transition Approach To High Temperature Superconductivity*, Imperial College Press, London, 2000
[18] T.Schneider and J.M.Singer, J.of Superconductivity **13**, 789 (2000)
[19] A.Fukuoka et al, Physica C **265**, 13 (1996)
[20] J. Hofer et al, Physica C **297**, 103 (1998)
[21] W.A. Groen et al, Physica C **165**, 55 (1990)
[22] T.R. Chien et al, Phys.Rev. B **49**, 1342 (1994)
[23] J.J. Neumeier et al, Phys.Rev.Lett. **63**, 2516 (1989)
[24] K.Kim and P.B.Weichman, Phys.Rev. B **43**, 13583 (1991)
[25] M.P.A. Fisher et al, Phys.Rev.Lett. **64**, 587 (1990)
[26] I.F. Herbut, Phys.Rev. B **61**, 14723 (2000)
[27] N. Babushkina et al, Physica C **185-189**, 901 (1991)
[28] H.J. Bornemann and D.E. Morris, Phys.Rev. B **44**, 5322 (1991)
[29] P. Franck et al, Phys.Rev. B **44**, 5318 (1991

FIG. 1. T_c and γ versus x for La_{2-x} Sr_xCuO_4. T_c data taken from [8-16]. The solid curve corresponds to $\gamma \propto \delta^{-\overline{\nu}}$ with $\overline{\nu} = 1$, $\delta = x - x_u$ and $x_u = 0.05$.

FIG. 2. Inverse isotope coefficient $1/\beta_{T_c}$ versus T_c/T_c^m for $La_{1.85}Sr_{0.15}Cu_{1-x}O_4$ [27], $YBa_{2-x}La_xCu_3O_7$ [28] and Y_{1-x} $Pr_xBa_2Cu_3O_7$ [29]. The straight line corresponds to Eq.(8) with $z\overline{\nu} = 1$ and $\overline{r} = 6$.

FIG. 3. Oxygen isotope effect for underdoped $La_{2-x}Sr_xCuO_4$ [6,7] in terms of $-T_c/\Delta T_c \propto 1/\beta_{T_c}$ versus $-\left(1/\lambda_{ab}^2(0)\right)/\Delta\left(1/\lambda_{ab}^2(0)\right) \propto \beta_{1/\lambda_{ab}^2}$. The solid line corresponds to $\beta_{d_s} = 0$ in Eq.(9) and the dashed one is a guide to the eyes. ● : taken from [6] and ■ : taken from [7].

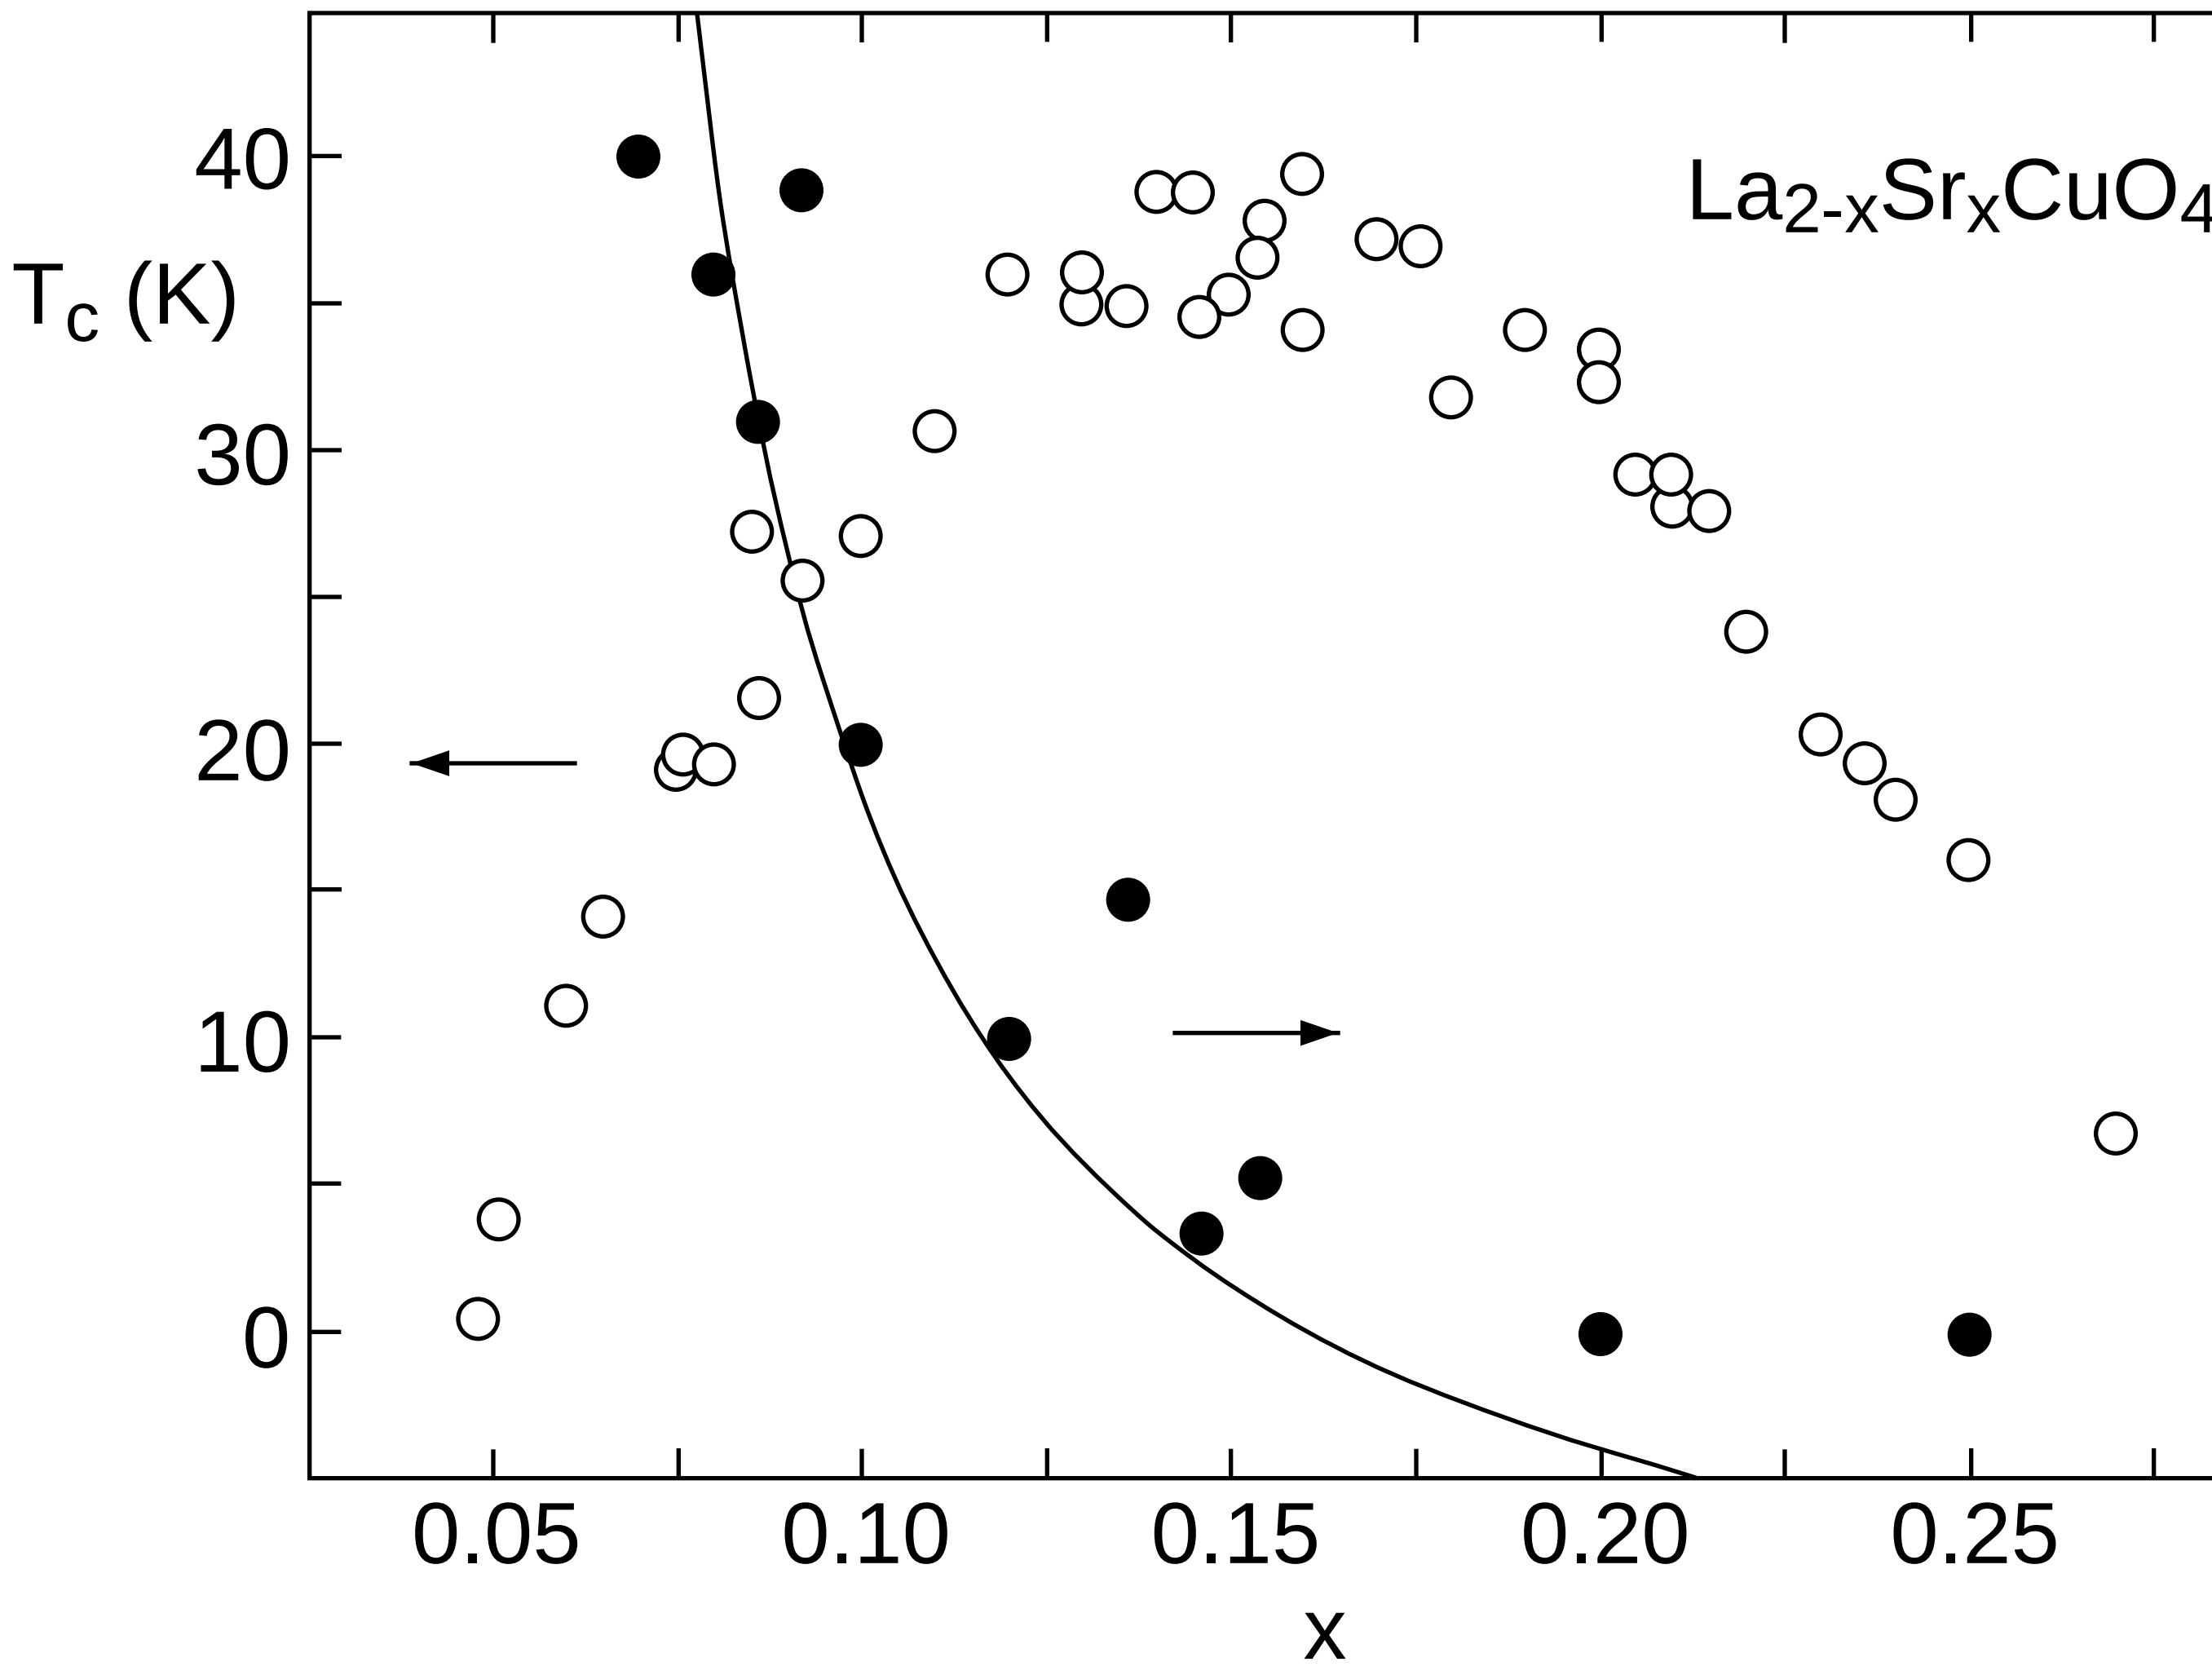
La2-xSrxCuO4
Tc (K)
40
30
20
10
0
0.05
0.10
0.15
0.20
0.25
x

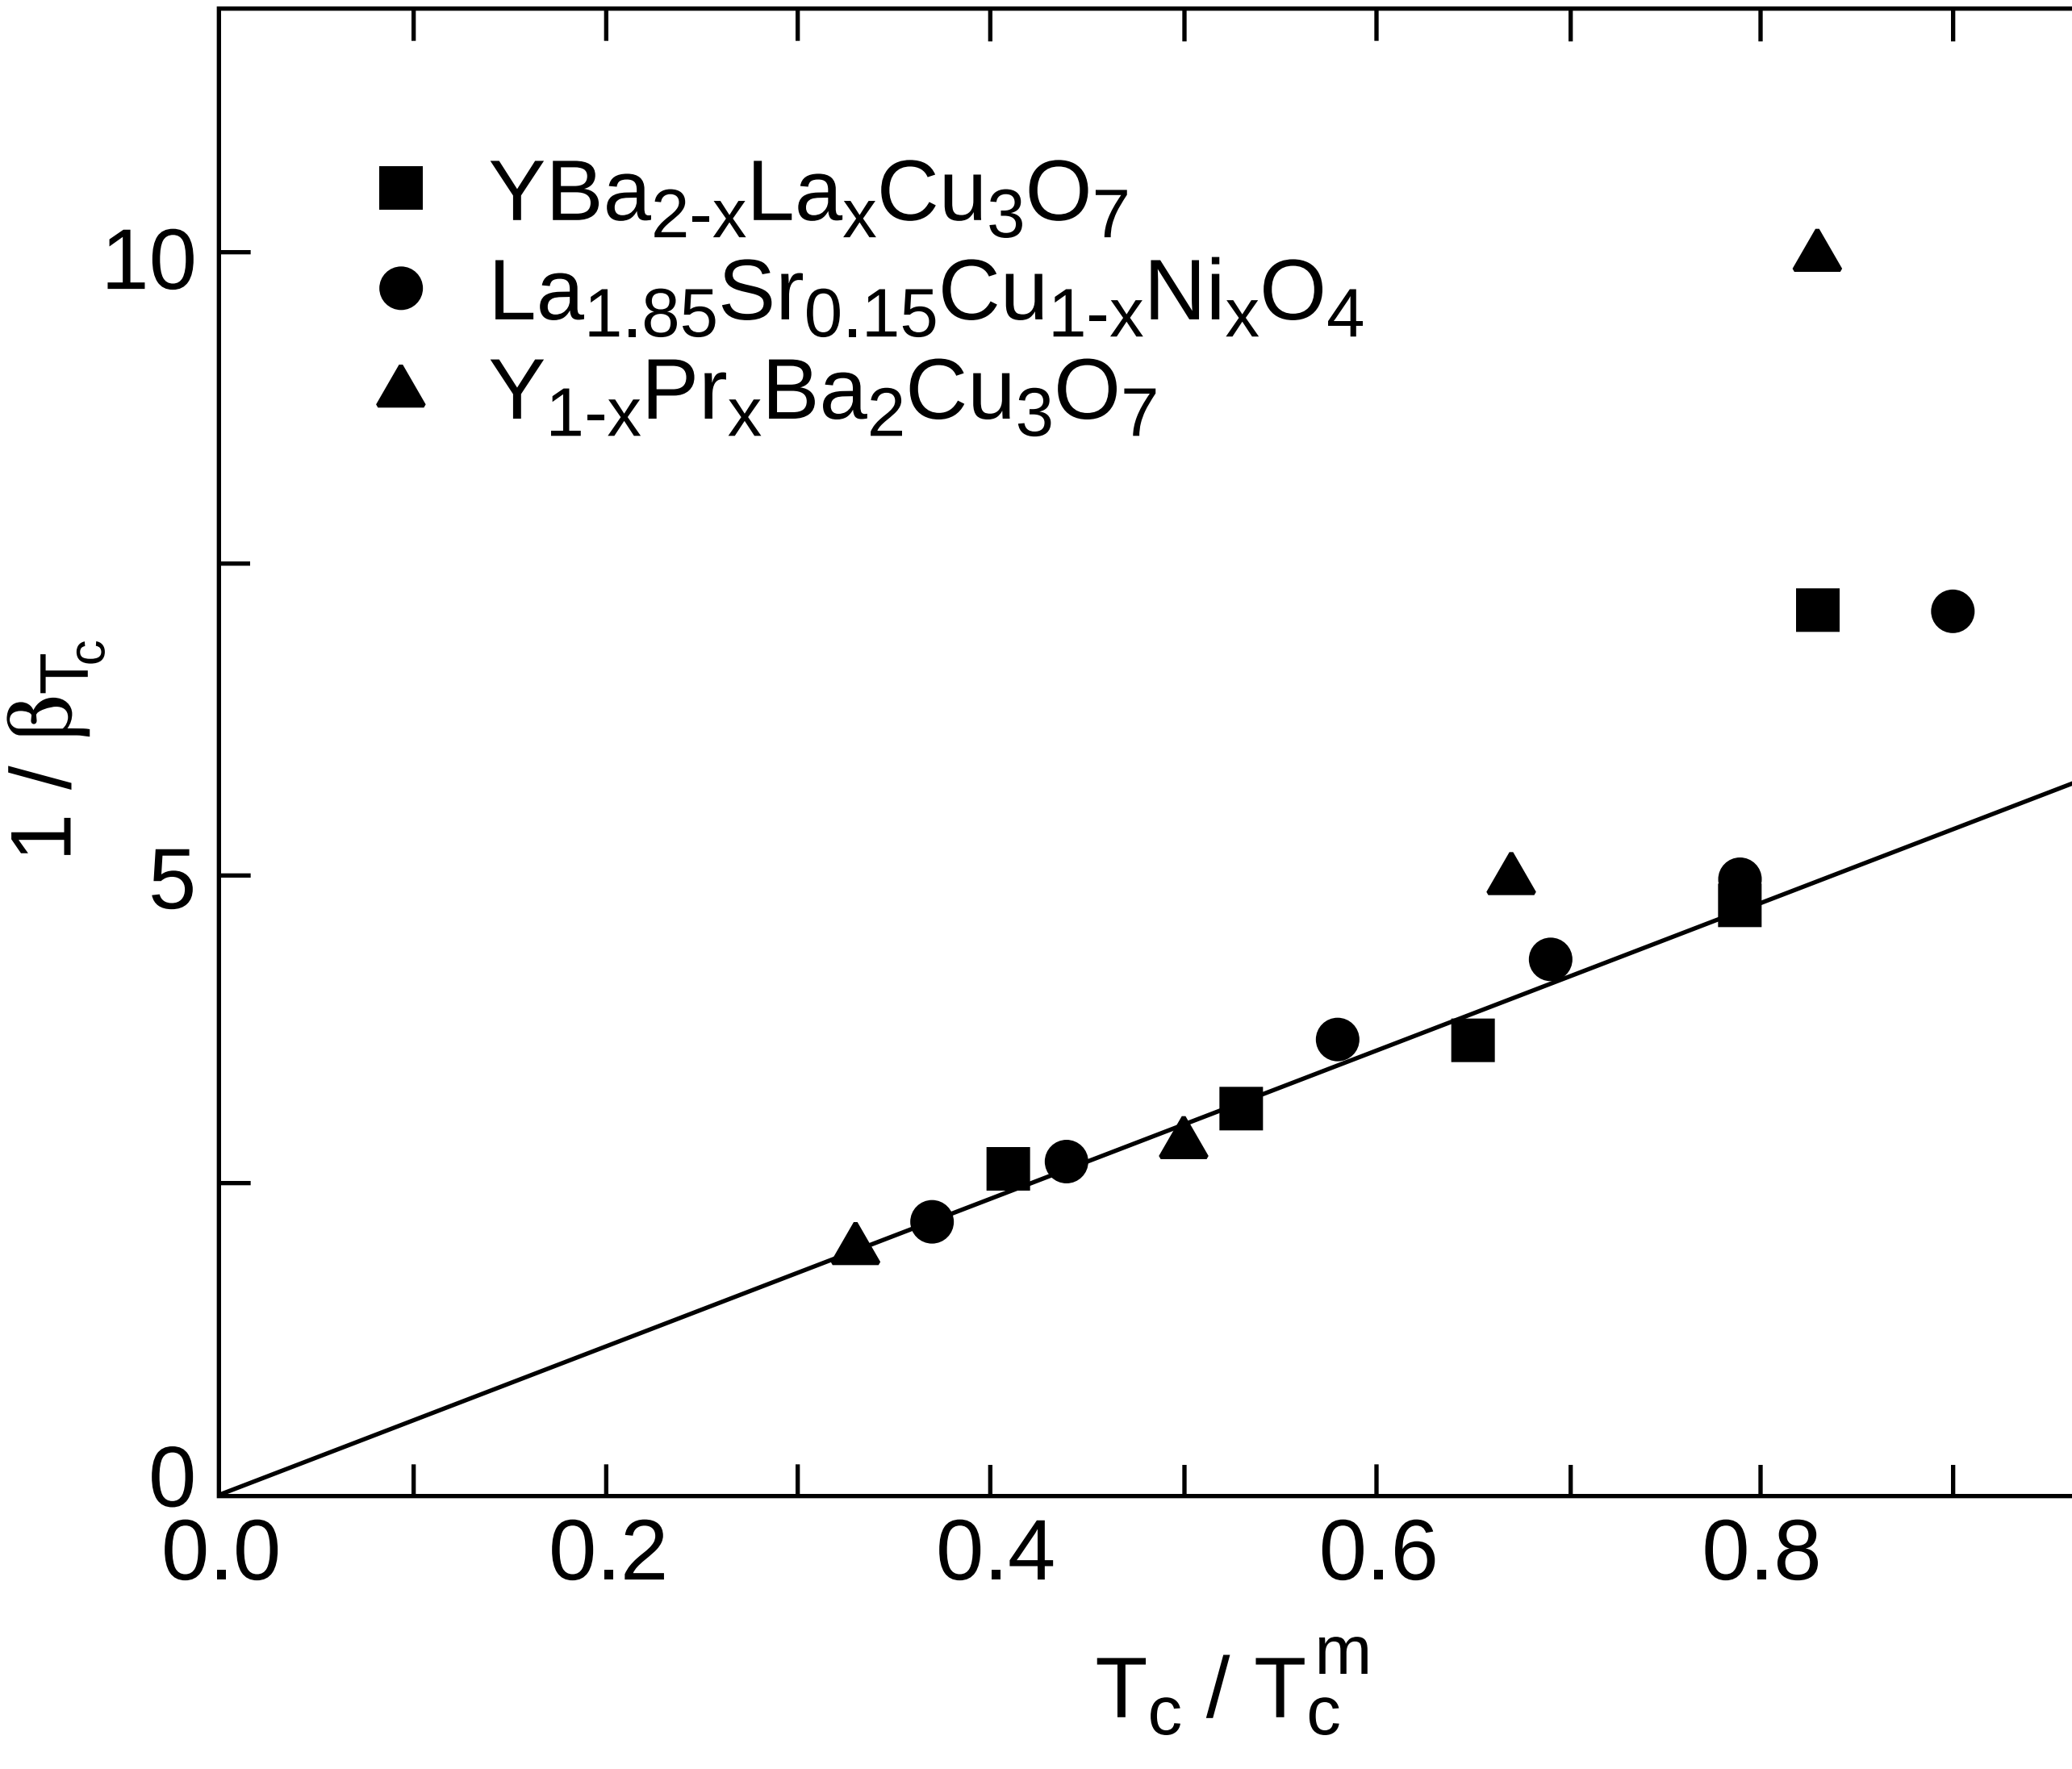
■ $YBa_{2-x}La_xCu_3O_7$
● $La_{1.85}Sr_{0.15}Cu_{1-x}Ni_xO_4$
▲ $Y_{1-x}Pr_xBa_2Cu_3O_7$
$1 / \beta_{T_c}$
0
5
10
0.0
0.2
0.4
0.6
0.8
T_c / T_c^m

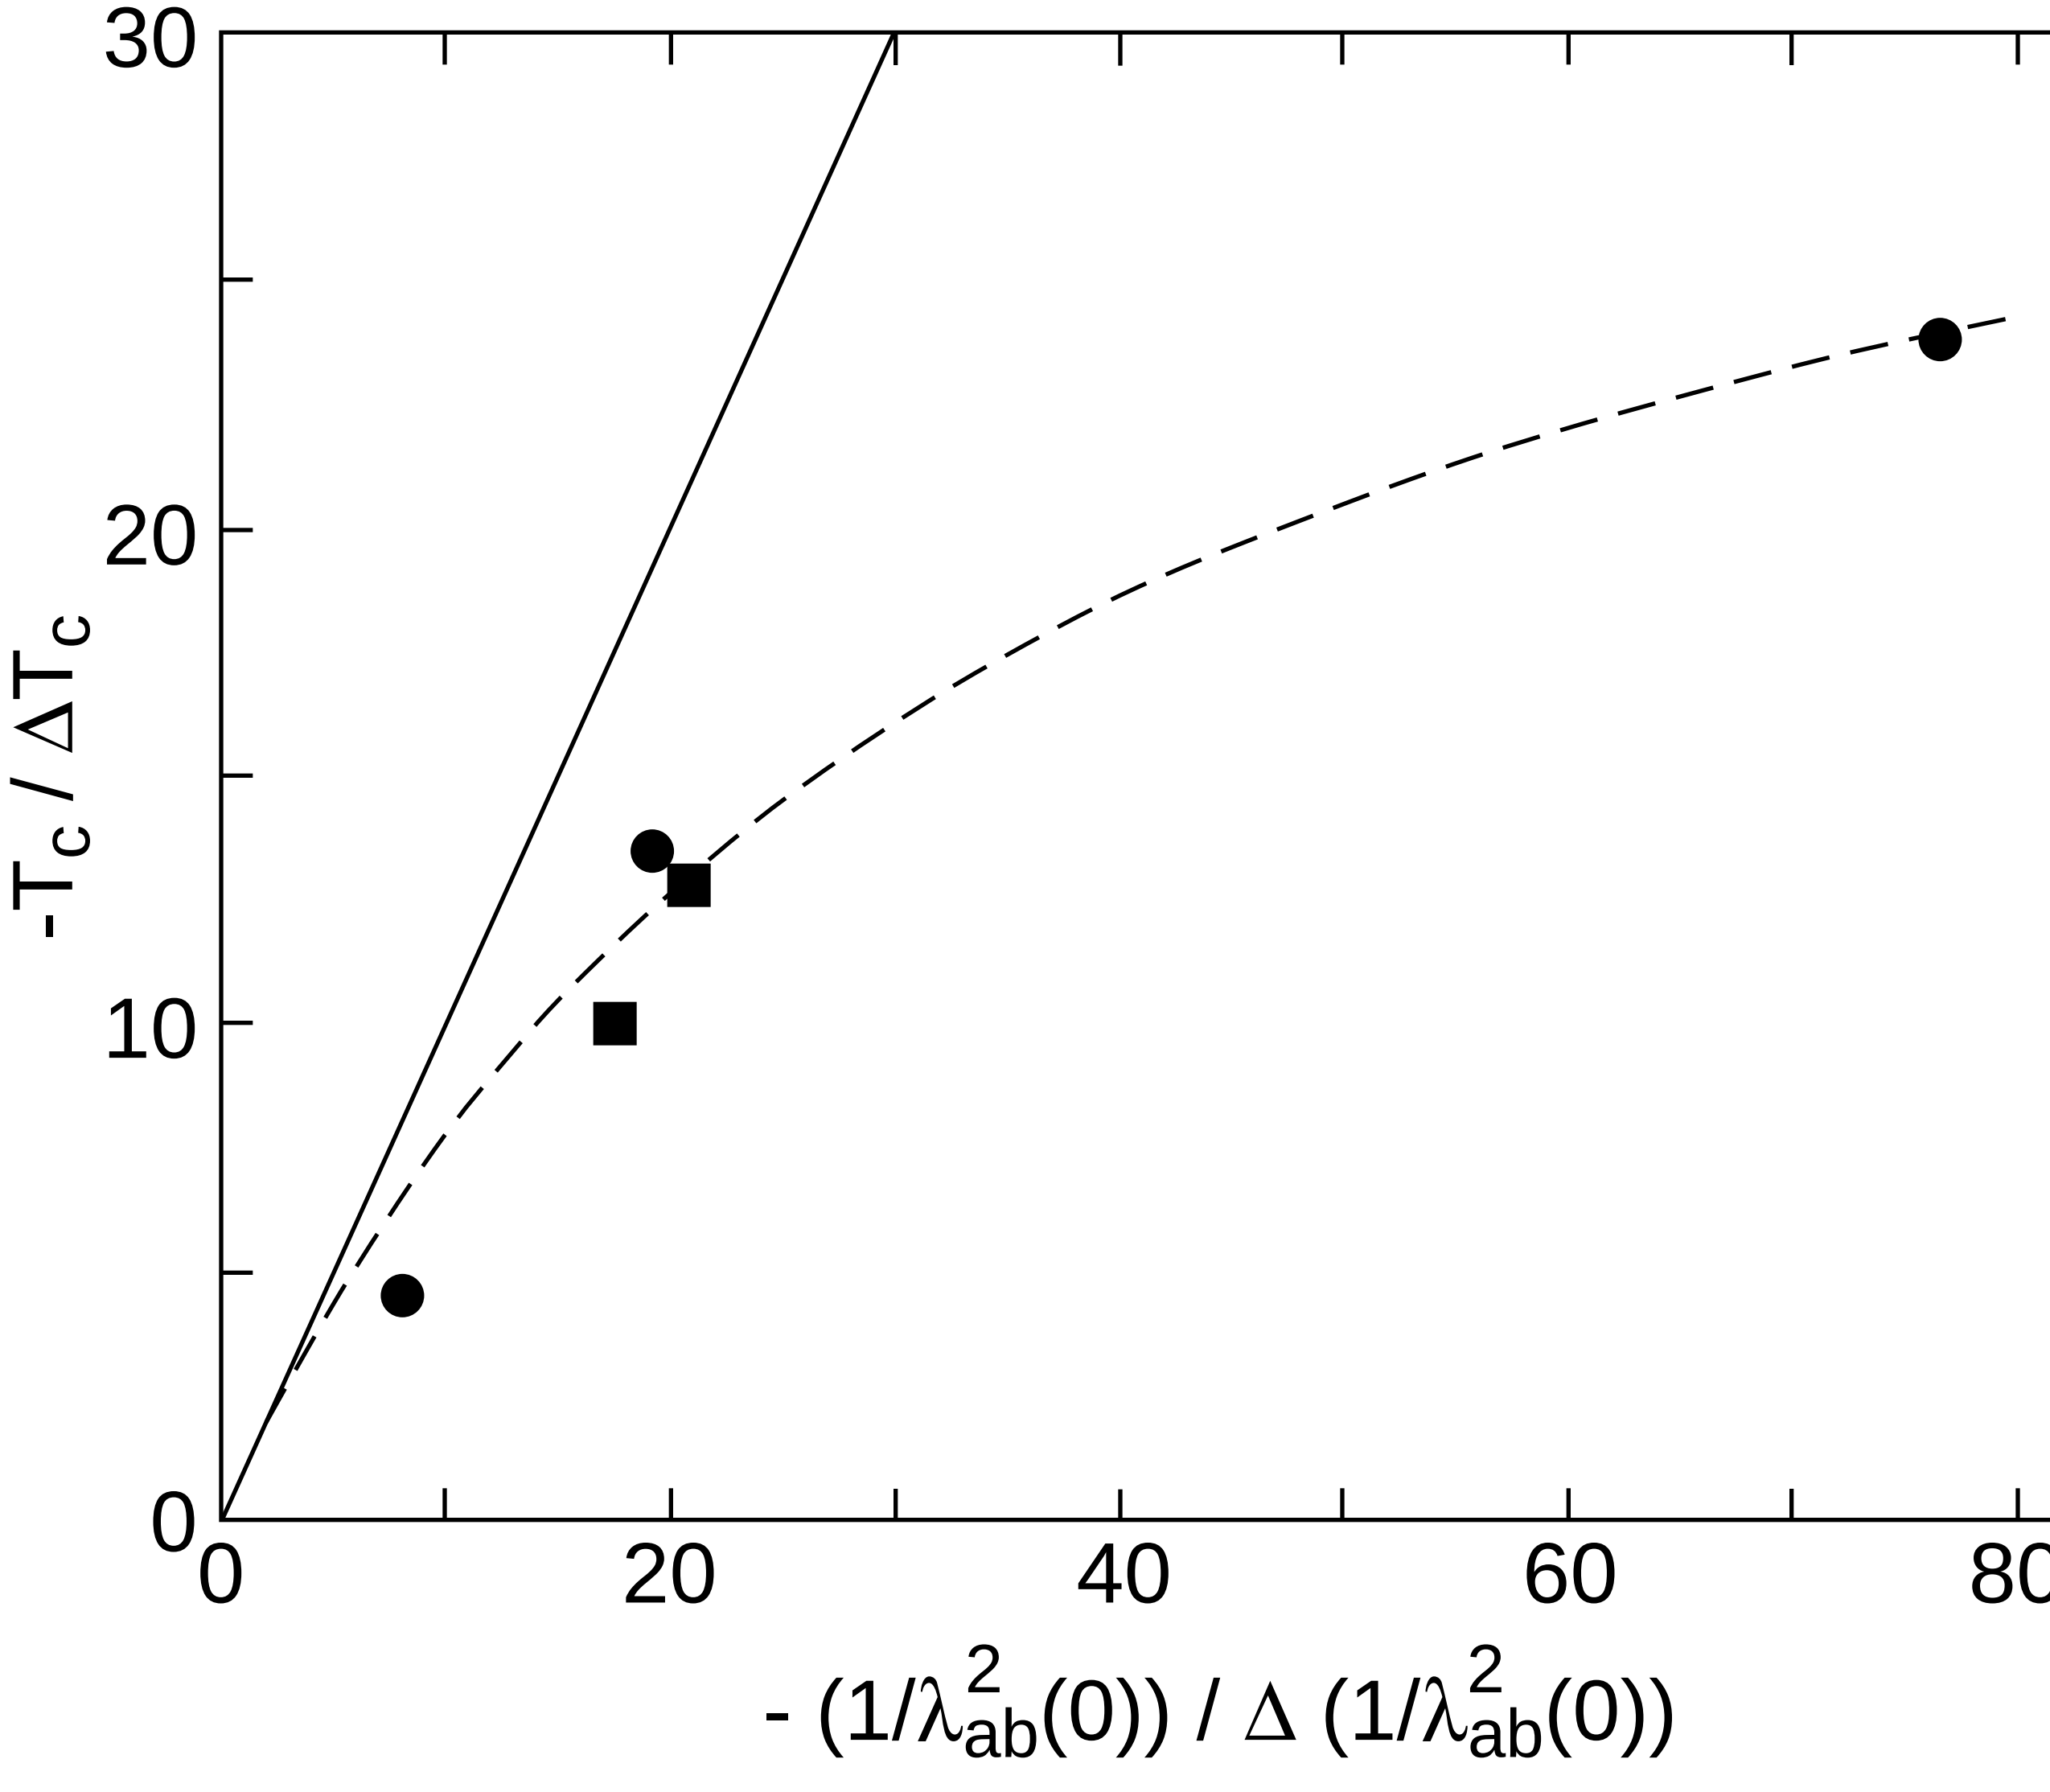
30
20
10
0
0
20
40
60
80
$-T_c / \Delta T_c$
$-(1/\lambda_{ab}^2(0)) / \Delta(1/\lambda_{ab}^2(0))$